

RSC Advances

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: M. Gisbert-Garzarán, D. Lozano, M. Vallet-Regí and M. Manzano, *RSC Adv.*, 2016, DOI: 10.1039/C6RA26771H.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

Self-Immolative Polymers as novel pH-responsive gate keepers for drug delivery

Received 00th January 20xx,
Accepted 00th January 20xxM. Gisbert^{a,b}, D. Lozano^{a,b}, M. Vallet-Regí^{a,b} * and M. Manzano^{a,b} *

DOI: 10.1039/x0xx00000x

www.rsc.org/

A novel pH-sensitive nanocarrier based on mesoporous silica nanoparticles with self-immolative polymers blocking the pore openings is presented. Triggered release by acid pH is demonstrated, together with their *in vitro* biocompatibility and effective cell internalisation, which makes this new material a promising candidate for future applications in cancer treatment.


Nanotechnology, which has the potential to impact nearly every area of modern society, is transforming medicine thanks to the development of new smart drug delivery systems.^{1–3} Those nanocarriers are expected to bring breakthroughs in terms of detecting, diagnosing and treating different forms of cancer.⁴ Recently, Mesoporous Silica Nanoparticles (MSNs) have drawn much attention for many biomedical applications, especially as drug delivery nanocarriers.^{5–10} The reason for that relays on their unique properties, such as a straightforward synthesis, a network of cavities ready available to be filled with different payloads, tuneable pore diameters and morphologies, facile surface functionalisation and hemo- and biocompatibility.^{11,12}

The textural properties of MSNs, such as large surface areas (*ca.* 1000 m²g⁻¹) and large pore volume (*ca.* 1 cm³g⁻¹), are responsible for their high loading capacities. In fact, conventional polymeric nanoparticles suffer from the drawback of low drug capacity, usually less than 5% of total weight, while MSNs allow much greater values.^{13,14}

However, MSNs present an open structure of the pores, which means that is simple to introduce molecules into their network of cavities, but it is also easy for them to diffuse out. This is the main reason to place gatekeepers on the entrance of the pores, so they can be closed once the cargo is loaded, and then opened to allow the drug release. The former process can be carried out during the production of the nanocarrier, but the later event, opening the gates of the pores, must be done

on-demand inside the body. This approach leads to stimuli-responsive nanocarriers,¹⁵ in which the release of the cargo is triggered by a stimulus than can be exogenous (temperature, light, magnetic fields or ultrasounds) or endogenous (pH, redox potential or specific enzymes or analytes). Those systems allow tailoring the release profiles with temporal and dosage control.

Among the available stimuli, pH variations offer the possibility of controlling the delivery of drugs to different regions of the body such as the gastrointestinal tract, the endosomes or lysosomes, or the tumour microenvironment. In particular, the slightly acidic lysosomal pH value (4.5–5)¹⁶ has been used for the design of pH-targeted nanocarriers that release their cargo once inside the cell.^{17,18} Then, an efficient pH-responsive system should respond to this subtle change of pH within this organelle, triggering the release of the cargo only inside the cells (Scheme 1).

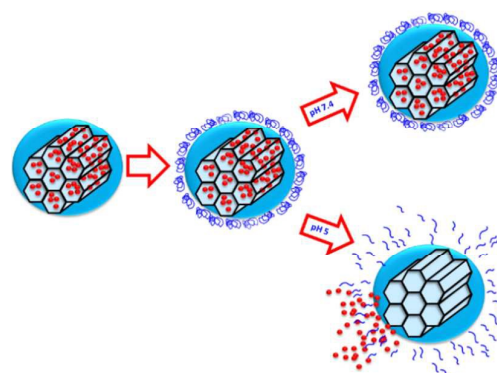

Scheme 1. Representation of the operating principle of our pH sensitive nanocarrier. A change in the pH initiates the disassembling of the self-immolative polymer allowing cargo molecules to diffuse out of the MSNs.

There are many polymeric systems with acid-sensitive bonds that can be exploited for designing responsive systems. In this sense, there are a new class of polymers, the so-called Self-Immolative Polymers (SIPs), that disassemble from head to tail completely when a specific functional group is cleaved from the polymer in response to certain stimuli.^{19,20} One potential

^a Departamento de Química Inorgánica y Bioinorgánica. Facultad de Farmacia. Universidad Complutense de Madrid, Instituto de Investigación Sanitaria Hospital 12 de Octubre i+12, Plaza de Ramón y Cajal s/n, E-28040 Madrid, Spain.


E-mail: vallet@ucm.es, mmanzano@ucm.es

^b Networking Research Center on Bioengineering, Biomaterials and Nanomedicine (CIBER-BBN), Madrid, Spain. Fax: +34913941786; Tel: +34913941861

Electronic Supplementary Information (ESI) available: See DOI: 10.1039/x0xx00000x



advantage is that it is possible to incorporate prodrugs into the polymer chain as pendant groups. These groups would turn into actual drugs as the self-immolation takes place.²¹ It is also possible to modify the rate at which the chain disassembles to achieve a more controlled and sustained drug release.²² There are many triggers that can initiate the fragmentation of the polymer into its building blocks, depending on the molecule placed at the end of the polymer. Thus, it is possible to design a linear polymer based on a polyurethane backbone with a pH sensitive capping molecule as trigger. Dropping the pH would cleavage the carbamate linkage of the trigger, which would start the sequential 1-6 elimination and decarboxylation reactions yielding CO₂ and the starting monomer. Combining both materials, MSNs and SIPs, in a single functional responsive nanocarrier would provide access to the benefits of both materials, *i.e.*, the high loading capacity of a variety of cargoes into MSNs, and the responsiveness of pH-sensitive SIPs to control the release. Decoration of the MSNs pore entrances with pH-responsive SIP gatekeepers that avoid premature release of the cargo and unblock the pores upon pH drops, represent a new and promising concept that is explored here for the first time (Scheme 2).

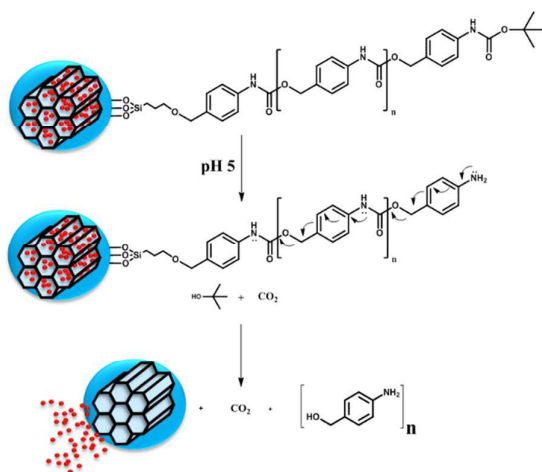

Scheme 2. Schematic representation of the nanocarrier response to acid pH. Cleavage of the protecting group generates an intermediate that undergoes sequential 1,6-elimination and decarboxylation reactions to form the initial monomer, disassembling the immolative polymer and allowing the cargo release.

In this work we have developed a smart nanocarrier able to respond to changes in the pH for potential applications in cancer treatment. For this purpose, we have selected MSNs as carriers and a SIP with a trigger sensitive to acid pH to block the pore entrances and prevent premature release. The pH sensitivity of the nanosystem was evaluated *in-vial* showing that cargo release took place in acidic conditions, while at physiological pH there was almost no release. The biocompatibility of the system was evaluated with different cells, and internalisation of the nanoparticles was also demonstrated.

MSNs were synthesised via sol-gel method under basic conditions using hexadecyltrimethylammonium bromide (CTAB) as structure directing agent following a previously

published method.²³ The sol-gel method allows a fine control on the final composition of the nanoparticles under mild conditions.^{24,25} The spherical morphology of the as-produced MSNs was confirmed through Scanning Electron Microscopy (SEM) and Transmission Electron Microscopy (TEM), as can be observed in Figure 1a and 1b, with average sizes of *ca.* 150 nm (see ESI, Figure S3 with Dynamic Light Scattering, DLS, studies).

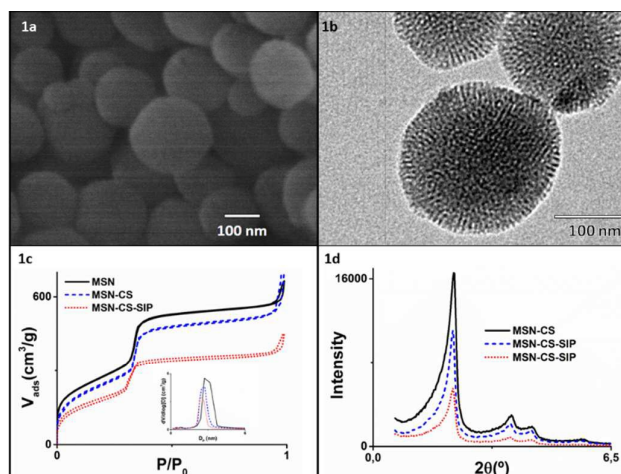


Figure 1. (a) SEM images of MSNs; (b) TEM images of MSNs; (c) Nitrogen adsorption and desorption isotherms of MSN (black solid line), MSN-CS (blue dashed line) and MSN-CS-SIP (red dotted line) (inset: pore size distribution determined by the BJH method from the desorption branch of the isotherm); (d) XRD patterns of MSN (black solid line), MSN-CS (blue dashed line) and MSN-CS-SIP (red dotted line).

Typical adsorption-desorption isotherms of MCM-41-like materials with cylindrical pores were observed (Figure 1c), with pore diameters centred at *ca.* 2.7 nm. The characteristic hexagonal arrangement of the pores was confirmed through low angle X-Ray Diffraction (XRD) analyses (Figure 1d), where typical well resolved maxima from well-ordered 2D-hexagonal structure with *p6mm* space group were observed.

A linear self-immolative polymer was produced to cover the pore entrances and avoid premature release of the cargo. We employed a polyurethane backbone with a BOC protecting group on the terminal amine that acted as a trigger. A pH drop would cleave the protecting group and initiate the disassembly of the polymer. The SIP was synthesised by a modification of a previously published method (Figure 2a),¹⁹ producing the monomer **1** from 4-aminobenzyl alcohol and phenyl chloroformate. Then, the polymerisation process using DBTL as catalyst and **2** as end-group led to the polymeric chain **3** with an average of about 20 monomers (determined by NMR, through the ratio benzylic hydrogens at the molecule tail *vs.* those in the polymeric backbone).

The self-immolative behaviour of the SIP was confirmed by treating the polymer with trifluoroacetic acid in CH₂Cl₂, which are the standard conditions for removing BOC protecting groups. After the acid treatment, all characteristic NMR peaks of SIP had disappeared (Figure S8), as expected.



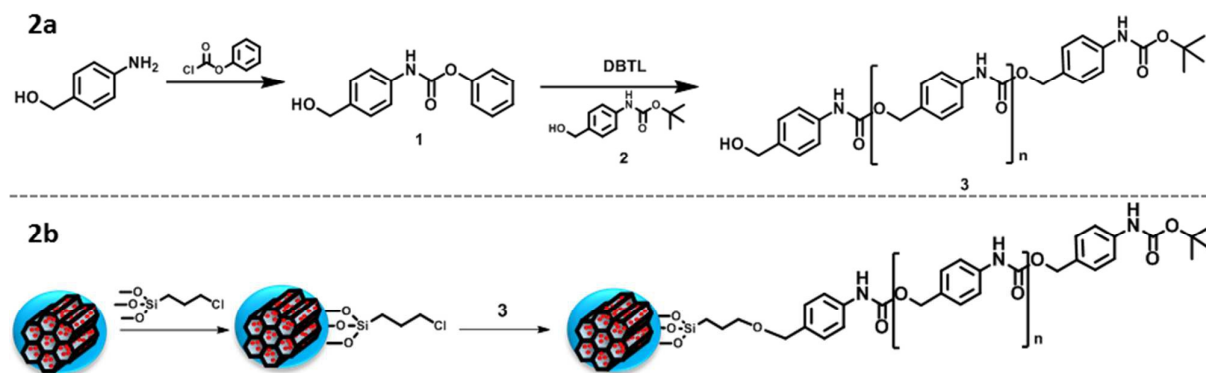


Figure 2. (a) Schematic representation of the SIP synthesis; (b) Schematic representation of the SIP grafting to the MSNs.

The successful attachment of the SIP to the MSNs was achieved through a previous modification of the nanoparticles with an alkoxy silane bearing chloride groups at the other end (denoted **CS**) (Figure 2b). Those modified-particles (**MSN-CS**) were characterised through thermogravimetric (TG) analysis (Fig. S1), where the increase of weight loss confirmed the presence of organic matter, together with elemental analysis (Table 1), where the increment of C % verifies the linker grafting. The C-H stretching bands from Fourier Transform Infrared spectroscopy (FTIR, Fig. S2) also confirmed the presence of the linker.

Addition of polymer **3**, previously activated with DIPEA, to the MSN-CS led to SIP coating (**MSN-CS-SIP**). XRD analyses after functionalisation (Figure 1d) showed that the ordered mesostructure survived the process, although the progressive reduction of the intensity might be ascribed to the partial filling of the pores by some polymer chains, as it was previously observed when functionalising MSNs with large dendrimers.²⁶ The successful SIP coating onto MSNs was confirmed through different characterisation techniques. The great weight loss observed in TG analyses (Fig. S1) is indicative of the great amount of SIP present. FTIR spectrum of MSN-CS-SIP (Fig. S2) exhibits additional bands to those typical from silica materials at *ca.* 1650 cm⁻¹, typical from C-O stretching vibrations from carbamates, verifying the presence of the polymer. This is in agreement with the data obtained from N₂ analyses (Table 1), in which the reduction of the surface area and pore volume is indicative of the presence of the polymer blocking the pore entrances. Finally, the increase of N % in the elemental analysis in MSN-CS-SIP confirms the presence of the polymer.

Table 1. Main properties of the materials produced in this work.

Material	MSN	MSN-CS	MSN-CS-SIP
Organic matter by TG (%)	5.3	14.4	20
Elemental analysis (%)			
C: 3.95	C: 9.34	C: 10.76	
H: 2.09	H: 2.34	H: 2.46	
N: 0.06	N: 0.11	N: 0.53	
Surface area (m ² /g)	1053	914	671
Pore Volume (cm ³ /g)	1.05	1.02	0.60
Pore width (nm)	2.74	2.66	2.19
Size (nm); PDI	190; 0.467	190; 0.467	190; 0.358
Zeta Potential (mV)	-35.3	-29.0	-23.8

Finally, the changes in the zeta potential to less negative values confirm the correct functionalisation. However, due to the small molecular weight of SIP the size was not affected by the functionalisation, either at pH 7.4 or pH 5.

After confirmation of the polymer grafting on the surface of MSN, drug delivery capabilities of the system were evaluated. Fluorescent cargo, tris(2,2'-bipyridine)dichloro ruthenium (II) denoted as **Ru**, was loaded into the network of cavities of the mesoporous nanoparticles overnight before the blocking the pore entrances with the SIP polymer (for further details see Supporting Information). The successful Ru loading was confirmed by the decrease in the pore volume measured through N₂ adsorption (data not shown).

The responsiveness to pH of the system here developed was evaluated through an *in-vial* Ru release from sample MSN-CS-SIP at 37°C using transwells at different pHs, *i.e.* 7.4 and 5. The data from the release kinetics, Figure 3, showed that there was almost no cargo release at physiological pH, which means that the nanocarrier would travel through the blood stream without premature release of the payload. However, when the pH of the solution dropped to pH 5, there was a fast release of the loaded Ru, as it can be observed in Figure 3. This behaviour confirmed that the polymer was disassembling as a consequence of the acid pH, opening the pore entrances and favouring the release of their cargo only at acid environments.

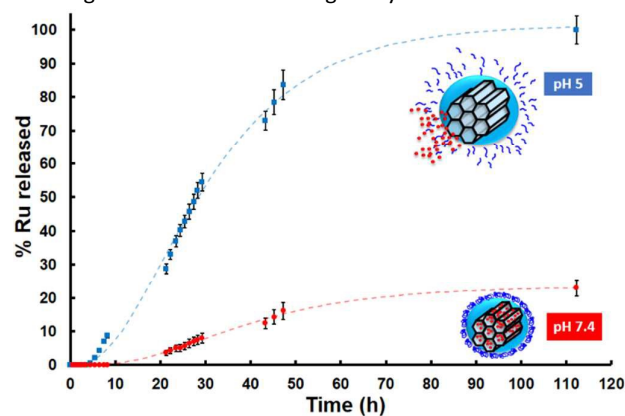


Figure 3. *In-vial* cumulative Ru release (in percentage) vs. time from MSN-CS-SIP at physiological and acid pHs (Repeated 3 times each measurement; Standard Error of the Mean (SEM)).



COMMUNICATION

Journal Name

Moreover, after being exposed to acid pH, the zeta potential of MSN-CS-SIP increased from -23.8 mV to -10.7 mV. That would confirm that the self-immolation actually took place, as its residue is a molecule of 4-aminobenzyl alcohol.

Once the MSNs covered with the SIPs nanocarrier were fully characterised and their pH-sensitive release capabilities demonstrated *in-vial*, the next step was analysing their behaviour with cells. The *in vitro* cytotoxicity study was determined by the exposition of MC3T3-E1 pre-osteoblastic cells to different amounts of nanoparticles (50, 100, 200 and 300 $\mu\text{g/mL}$). Figure 4 shows that none of the studied concentrations, except 300 $\mu\text{g/mL}$, induced significant cytotoxicity measured by an Alamar Blue assay (cell viability was > 99% that of the control). Similar results were obtained in LNCaP tumoral cells (Figure S9).

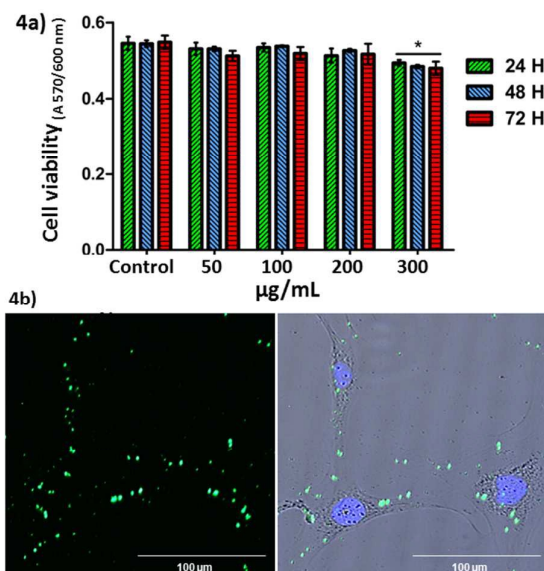


Figure 4. (a) MC3T3-E1 cell viability in contact with different concentrations of nanoparticles at 24, 48 and 72h of cell culture. Similar proliferation results were obtained in LNCaP cells. * $p < 0.05$ vs control without nanoparticles (Student's *t*-test). (b) Fluorescence microscopy images of LNCaP cells incubated with nanoparticles at 2 hours of cell culture. From left to right: green fluorescence (nanoparticles with fluorescein) and overlay image with blue fluorescence (nuclei).

Cellular internalization of the nanoparticles was observable by fluorescence microscopy and analyzed by flow cytometry in LNCaP cells in contact with the nanoparticles (100 $\mu\text{g/mL}$) for 2 hours. No fluorescence was observed in the end slices corresponding to the external cellular surfaces, suggesting that the nanoparticles did not adsorb on the cell membranes. Therefore, we observed that the nanoparticles at 100 $\mu\text{g/mL}$ were internalized by LNCaP cells. The cellular uptake observed by fluorescence microscopy was also confirmed by flow cytometry (19.25 \pm 1.5% of nanoparticles incorporation) in the same cells, at 2 hours. The low cellular internalization would be in agreement with the fact that positively charged²⁷ or targeted²⁸ nanocarriers show better cellular internalization than those negative, as in the case of MSN-CS-SIP.

Conclusions


In conclusion, we have developed for the first time Mesoporous Silica Nanoparticles capped with acid responsive Self-Immolative Polymers. The cargo release can be triggered by acid pH, typical from tumours microenvironments. The biocompatibility of this new delivery nanoplatform has been demonstrated with different cell types, and the effective nanoparticle internalization has been achieved in tumoral cells. We envision that the synergy from MSNs carriers and SIPs could be of a great interest for future applications in nanomedicine to fight against cancer.

The authors thank funding from the EU H2020-NMP-PILOTS-2015 program through the grant no. 685872 (MOZART) and the European Research Council (Advanced Grant VERDI; ERC-2015-AdG Proposal no. 694160). D. Lozano is recipient of postdoctoral research contract from Ministerio de Economía y Competitividad (FPDI-2013-17268), Spain.

Notes and references

- O. C. Farokhzad and R. Langer, *ACS Nano*, 2009, **3**, 16–20.
- J. D. Byrne, T. Betancourt and L. Brannon-Peppas, *Adv. Drug Deliv. Rev.*, 2008, **60**, 1615–1626.
- S. Mura, J. Nicolas and P. Couvreur, *Nat. Mater.*, 2013, **12**, 991–1003.
- R. Misra, S. Acharya and S. K. Sahoo, *Drug Discov. Today*, 2010, **15**, 842–850.
- A. Baeza, M. Manzano, M. Colilla and M. Vallet-regí, *Biomater. Sci.*, 2016, **4**, 803–813.
- F. Tang, L. Li and D. Chen, *Adv. Mater.*, 2012, **24**, 1504–1534.
- Z. Li, J. C. Barnes, A. Bosoy, J. F. Stoddart and J. I. Zink, *Chem. Soc. Rev.*, 2012, **41**, 2590.
- C. E. Ashley, E. C. Carnes, G. K. Phillips, D. Padilla, P. N. Durfee, P. a Brown, T. N. Hanna, J. Liu, B. Phillips, M. B. Carter, N. J. Carroll, X. Jiang, D. R. Dunphy, C. L. Willman, D. N. Petsev, D. G. Evans, A. N. Parikh, B. Chackerian, W. Wharton, D. S. Peabody and C. J. Brinker, *Nat. Mater.*, 2011, **10**, 389–397.
- I. I. Slowing, J. L. Vivero-Escoto, B. G. Trewyn and V. S.-Y. Lin, *J. Mater. Chem.*, 2010, **20**, 7924–7937.
- M. Manzano and M. Vallet-Regí, *J. Mater. Chem.*, 2010, **20**, 5593.
- B. G. Trewyn, I. I. Slowing, S. Giri, H. Chen and V. S. Lin, *Acc. Chem. Res.*, 2007, **40**, 846–853.
- J. L. Vivero-Escoto, I. I. Slowing, B. G. Trewyn and V. S.-Y. Lin, *Small*, 2010, **6**, 1952–1967.
- C. Argyo, V. Weiss, C. Bräuchle and T. Bein, *Chem. Mater.*, 2014, **26**, 435–451.
- Y. Zhang, Z. Zhi, T. Jiang, J. Zhang, Z. Wang and S. Wang, *J. Control. Release*, 2010, **145**, 257–263.
- A. Baeza, M. Colilla and M. Vallet-Regí, *Expert Opin. Drug Deliv.*, 2015, **12**, 319–337.
- T. Kolter and K. Sandhoff, *FEBS Lett.*, 2010, **584**, 1700–1712.
- Z. Li, H. Li, L. Liu, X. You, C. Zhang and Y. Wang, *RSC Adv.*, 2015, **5**, 77097–77105.
- Y. Yan, J. Fu, X. Liu, T. Wang and X. Lu, *RSC Adv.*, 2015, **5**, 30640–30646.
- A. Sagi, R. Weinstein, N. Karton and D. Shabat, *J. Am. Chem. Soc.*, 2008, **8**, 5434–5435.
- W. Wang and C. Alexander, *Angew. Chemie - Int. Ed.*, 2008, **47**, 7804–7806.
- S. Gnaïm and D. Shabat, *Acc. Chem. Res.*, 2014, **47**, 2970–2984.
- R. A. McBride and E. R. Gillies, *Macromolecules*, 2013, **46**, 5157–5166.
- A. Baeza, E. Guisasaola, A. Torres-Pardo, J. M. González-Calbet, G. J. Melen, M. Ramirez and M. Vallet-Regí, *Adv. Funct. Mater.*, 2014, **24**, 4625–4633.
- A. S. Timin, A. R. Muslimov, K. V. Lepik, N. N. Saprykina, V. S. Sergeev, B. V. Afanasyev, A. D. Vilesov and G. B. Sukhorukov, *J. Mater. Chem. B*, 2016, **18**, 33–37.
- A. S. Timin, H. Gao, D. V. Voronin, D. A. Gorin and G. B. Sukhorukov, *Adv. Mater. Interfaces*, 2016.
- B. Gonzalez, M. Colilla, C. L. de Laorden and M. Vallet-Regí, *J. Mater. Chem.*, 2009, **19**, 9012–9024.
- A. Verma and F. Stellacci, *Small*, 2010, **6**, 12–21.
- K. Ulbrich, K. Holá, V. Šubr, A. Bakandritsos, J. Tuček and R. Zbořil, *Chem. Rev.*, 2016, **116**, 5338–5431.



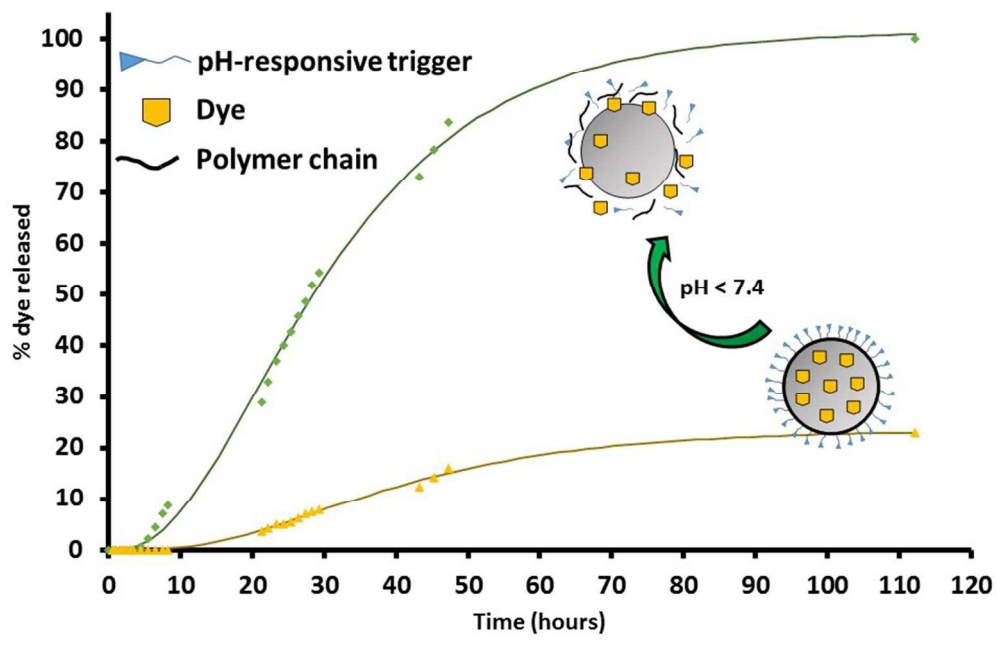

254x190mm (96 x 96 DPI)

